

## Binder Jet Line Nickel 718

Parameters and Processes for Colibrium Additive Binder Jet Line



### Nickel Alloy 718 (2.4668)


Nickel chromium superalloys like Nickel 718 are often used in high-stress and high-temperature environments. The excellent high-temperature strength and creep resistance of this alloy derive from precipitation hardening which creates finely dispersed precipitates.

Nickel 718 is a metal that is also highly resistant to the corrosive effects of hydrochloric acid and sulfuric acid. The favorable weldability of Nickel 718 makes this alloy suitable for standard post-processing activities. Typical applications are high-quality components designed for thermally-challenging environments such as rocket engines and gas turbine hot sections.

### Nickel 718 (2.4668) Binder Jet

Through mechanical testing and bulk material characterization, this parameter and the applied post-processing route demonstrated properties that exceed cast requirements and match MIM minimums.

Compared to other powder bed additive manufacturing processes, binder jet offers economy of scale for customers requiring both part quantity and part variation with favorable cost: a build box 0.5 meters per side can be fully printed in approximately 18 hours.

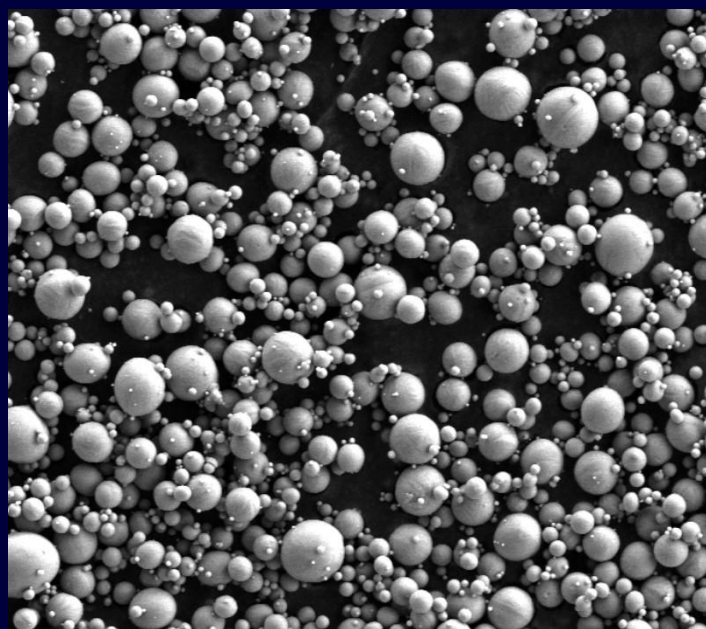

# Binder Jet Line Nickel 718 (2.4668)

## Machine Configuration

---

Colibrium Additive Binder Jet Line

Air Atmosphere

Aqueous Binder

## Powder Chemistry

---

Nickel 718 powder conforms to AMS 5383

## Parameter Information

---

This build parameter utilizes a 75  $\mu\text{m}$  layer thickness and green parts are sintered for 600 minutes at 1320°C after a curing step. Sinter cycle optimization is encouraged for thin section parts.

## Thermal States

---

The post-processing route for this material was a three-step HIP + solution + age:

- Hot Isostatic Press (HIP): 1162°C for 4 hours at 100 MPa
- Solution: 1050°C for 1 hour
- Age: 718°C for 8 hours followed by furnace cooling to 621°C for 8 hours

## Residual Carbon & Nominal Chemistry

---


The carbon concentration after the full heat treatment met casting (AMS 5383) and MIM (AMS 5917) specification maximums.

Additionally, all other constituents were measured post-sinter and observed to be within AMS 5383 limits.

## Porosity

---

The average porosity after the full heat treatment was approximately 0.2% in parts with varying wall thicknesses (2 – 20 mm)

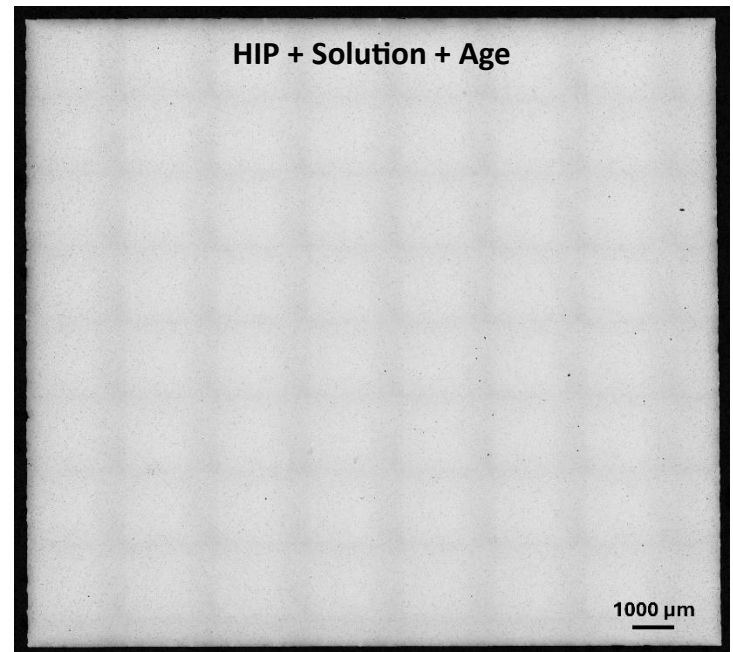

Figures and data contained herein are approximate and/or typical only and are dependent on several factors including but not limited to process and machine parameters. The information provided on this material data sheet is illustrative only and cannot be considered binding.

## Tensile Performance at Room Temperature

	0.2% Yield Strength (MPa)		Ultimate Tensile Strength (MPa)	
	H	V	H	V
HIP+SOLN+AGE	1045	1045	1260	1262

	Elongation (%)		Area Reduction (%)	
	H	V	H	V
HIP+SOLN+AGE	21	21	31	31

## Tensile Performance at 535°C

	0.2% Yield Strength (MPa)		Ultimate Tensile Strength (MPa)	
	H	V	H	V
HIP+SOLN+AGE	895	893	1038	1036

	Elongation (%)		Area Reduction (%)	
	H	V	H	V
HIP+SOLN+AGE	20	19	36	33

## Tensile Performance at 650°C


	0.2% Yield Strength (MPa)		Ultimate Tensile Strength (MPa)	
	H	V	H	V
HIP+SOLN+AGE	855	859	982	995


	Elongation (%)		Area Reduction (%)	
	H	V	H	V
HIP+SOLN+AGE	14	14	19	17

Figures and data contained herein are approximate and/or typical only and are dependent on several factors including but not limited to process and machine parameters. The information provided on this material data sheet is illustrative only and cannot be considered binding.

## Axial Low-Cycle Fatigue (Machined Surfaces, H + V) at 315°C and R = 0

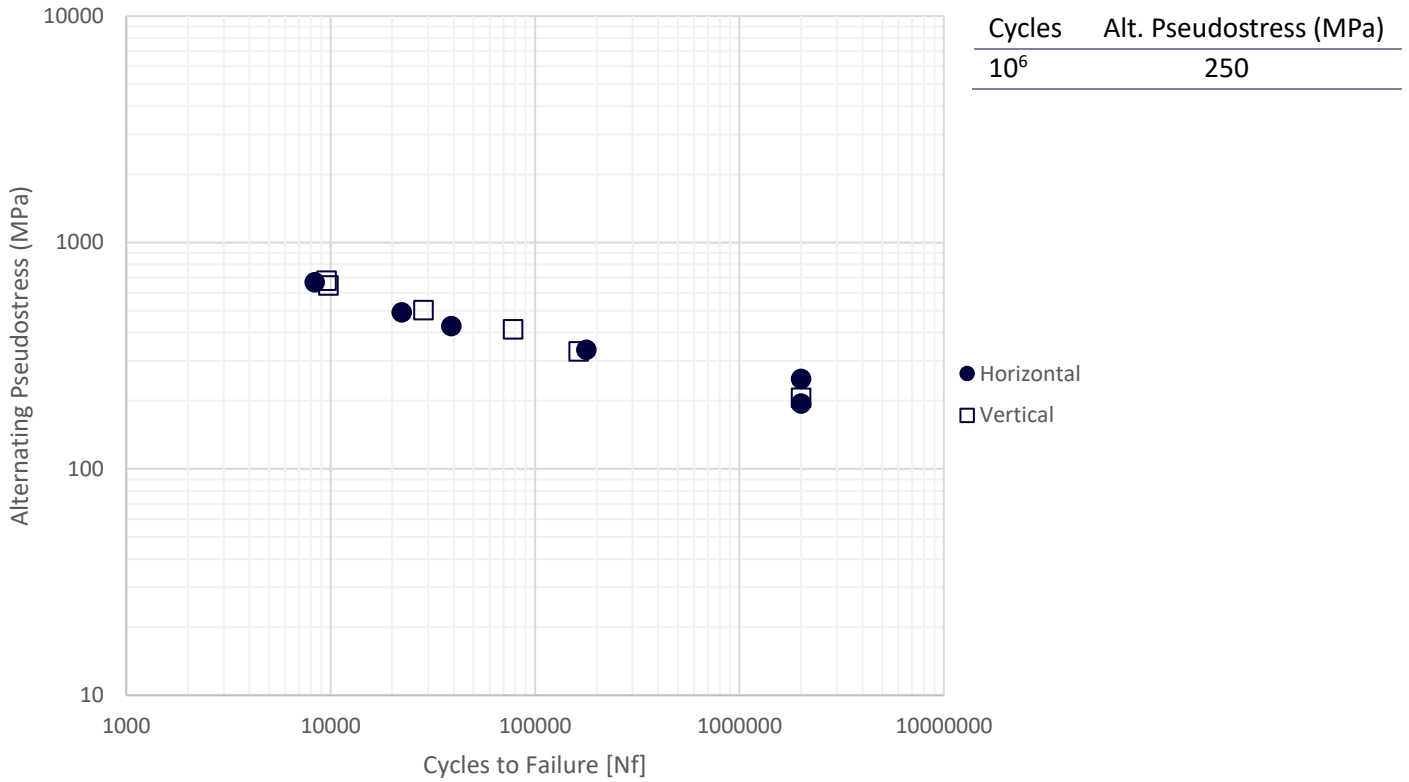

## Microstructure (Etched)

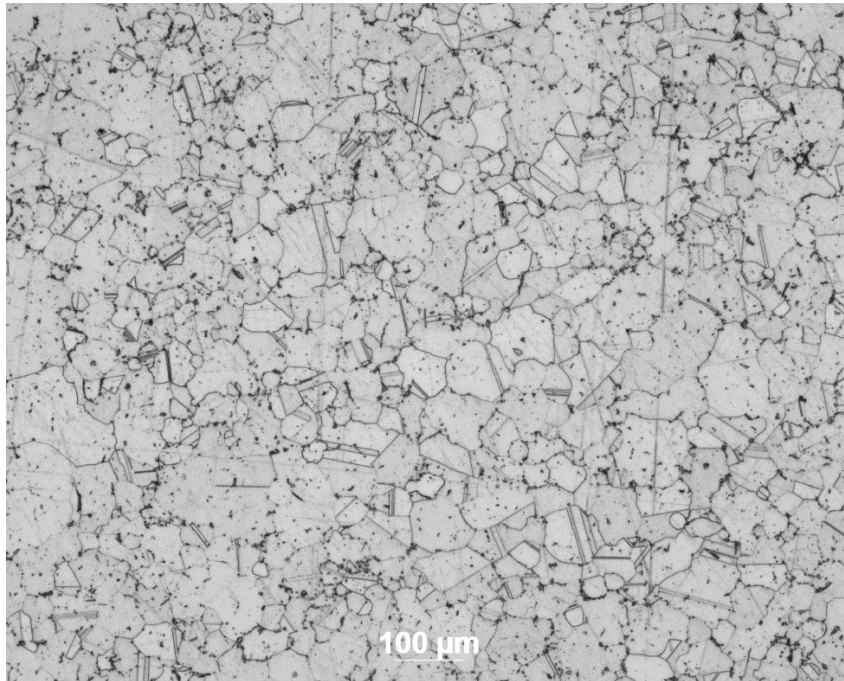

Vertical, HIP + SOLN + AGE

Figures and data contained herein are approximate and/or typical only and are dependent on several factors including but not limited to process and machine parameters. The information provided on this material data sheet is illustrative only and cannot be considered binding.

## Data Sheet Nomenclature and Notation

---

H: Horizontal, X or Y.

V: Vertical, Z.

Other angles are measured from horizontal.

Compositional testing was performed according to ASTM E1447 and E1097.

Tensile evaluations were performed via ASTM E 8 and E 21. All surfaces were machined prior to testing.

Axial low cycle fatigue characterization was performed via ASTM E 606. All surfaces were machined prior to testing.

Figures and data contained herein are approximate and/or typical only and are dependent on several factors including but not limited to process and machine parameters. The information provided on this material data sheet is illustrative only and cannot be considered binding.